

.....
Topics

Standardization Activities of Reliability Evaluation Methods for High-Capacitance Multilayer Ceramic Capacitors in TWA24

Adachi Yutaka ^{1*}

¹ Electroceramics Group, Research Center for Functional Materials
 National Institute for Materials Science (NIMS)

High-capacity multilayer ceramic capacitors (MLCCs) are essential electronic components for modern electronic devices. For example, smartphones and notebook PCs contain approximately 800 to 900 MLCCs per unit. For use in automotive and aerospace applications, MLCCs require superior characteristics not only for chip size, capacitance, and temperature stability, but also for reliability. However, there is still no standardization of reliability evaluation methods for MLCCs. In light of this situation, the VAMAS Technical Working Area TWA24 began in 2016 to develop a draft standardization proposal for reliability evaluation and analysis methods for MLCCs. After several domestic round-robin tests (RRT), an international RRT was conducted in 2019 with the participation of 6 institutions, and then it was confirmed that the proposed evaluation and analysis methods are effective for reliability evaluation of MLCCs. This paper presents the background and results of this international RRT.

1. Introduction

High-capacitance multilayer ceramic capacitors (MLCCs) are electronic components used in almost all electronic devices for noise suppression and voltage stabilization. MLCCs are capacitors with a multi-layered structure of dielectric layers and internal electrodes, as shown in Figure 1, and the capacitance can be increased by making the dielectric layers thinner or increasing the number of layers to increase the specific surface area of the electrodes. The miniaturization of electronic devices and the increase in the number of integrated circuit chips per unit area have led to demands for smaller size and higher capacitance of MLCCs. At present, MLCCs with the size of 0201 (0.2 mm × 0.1 mm) are manufactured.

International standards have already been established for MLCCs, including those for chip size, capacitance, and temperature stability¹⁾. However, there is still no standardization on the reliability evaluation method of MLCCs and the prediction of product lifetime. With the spread of electric vehicles and the increasing sophistication of autonomous driving, more and more MLCCs are expected to be used for automotive applications, and higher reliability is required for MLCCs used in automotive applications than

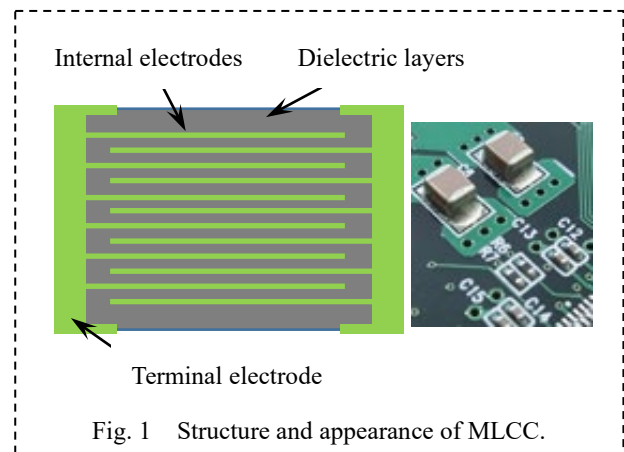


Fig. 1 Structure and appearance of MLCC.

those used in general electronic devices. Therefore, the standardization of MLCC reliability evaluation methods will be beneficial to both MLCC manufacturers and users.

2. Standardization activities in TWA24

The MLCC Reliability Evaluation Committee, chaired by Prof. Tsurumi of Tokyo Institute of Technology, was established in 2016 and started activities to standardize the reliability test methods for MLCCs. This committee was set up as part of the standardization activities of the VAMAS Technical Working Area TWA24, and four major Japanese MLCC manufacturers, Murata Manufacturing Co., Ltd.,

*E-mail: adachi.yutaka@nims.go.jp

Taiyo Yuden Co., Ltd., TDK Corporation, and Kyocera Corporation, participated in the committee.

Several local round robin tests (RRTs) were conducted by this committee to identify the causes of differences in lifetime prediction. As a result, by the end of 2018, we obtained reasonable results from all the companies, and then we prepared the first draft of a reliability evaluation and analysis method. The international RRT using this test method was approved at the 44th VAMAS Steering Committee Meeting held in Boulder, USA, in May 2019.

After that, we invited more organizations to participate in the international RRT, and two companies, Samsung Electronics Co. (Korea) and Yageo/KEMET (Taiwan/USA), joined us in addition to the four Japanese companies that had participated in the MLCC Reliability Evaluation Committee. In August 2019, 1000 units of Murata MLCCs (22 uF and 1608 mm chip size) from the same production lot and the measurement procedure manual describing how to set up samples and measurement conditions were sent to each participating company to start the international RRT.

3. MLCC reliability evaluation method

The reliability evaluation method used in this RRT is as follows. There are various reliability requirements for MLCCs, but the property targeted in this RRT is the reliability of insulation resistance. Since a MLCC is an electrical insulator, almost no current flows when a DC voltage is applied. However, if voltage is applied for a long period of time, the current will increase at a certain point, eventually leading to dielectric breakdown. In this RRT, the MLCC lifetime was defined as the time to reach a current value 100 times higher than the initial current value.

For reliability evaluation of MLCCs, the Highly Accelerated Life Test (HALT) is usually used because it provides results in a short time. In HALT, the leakage current of a sample at a higher temperature and voltage than the normal operating environment is measured, and then time to result in dielectric breakdown is obtained. In this study, accelerated tests were conducted using 100 samples under the 5 different measurement conditions shown in Figure 2. The results were subjected to Weibull statistical analysis²⁾, and the average lifetime η was calculated for each measurement condition.

The reason for performing the measurements under 5 different temperature and voltage conditions is to obtain the

	6.3 V	9.5 V	12.6 V
140 °C		✓	
150 °C	✓	✓	✓
160 °C		✓	

Fig. 2 Measurement temperatures and applied voltages used in this RRT.

parameters, the voltage acceleration constant N and the activation energy E_a , which are necessary to determine the lifetime under actual operating temperature and voltage. By applying these values to the Eyring equation, the lifetime can be calculated under actual operating temperatures and voltages.³⁾ In this RRT, η under each measurement condition, calculated N , E_a , and product lifetime under reference conditions (85°C, 6.3V) were collected from each organization.

The variation of η among participating institutions under each measurement condition was relatively small, ranging from 8.6 to 12.6 %. Figure 3 shows N , E_a , and product lifetime under reference conditions (85°C, 6.3V) calculated from these results. The variation of N and E_a among participating institutions was small, 6.5 % in both cases, indicating that the proposed measurement procedure was valid. On the other hand, the product lifetime under the reference conditions calculated using these values varied largely, with a coefficient of variation of 24.7 %. Since the product lifetime under reference conditions was calculated using η , N , and E_a under each measurement condition, it was considered that errors in these parameters were propagated, resulting in a larger variation.

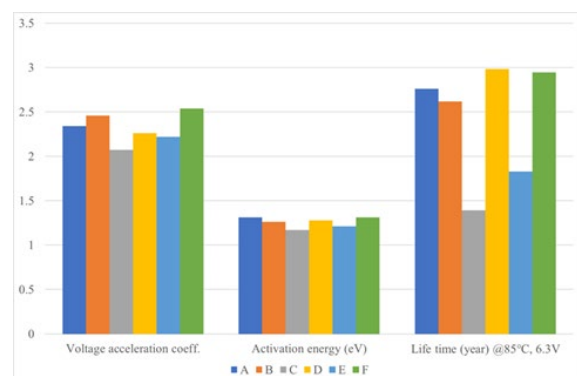


Fig. 3 Voltage acceleration factor, activation energy and product lifetime under reference conditions (85°C, 6.3V).

4. summary

In this paper, we have briefly described the international RRT for standardization of MLCC reliability evaluation methods. The values of η , N , and E_a obtained in this RRT show little variation among participating institutions, indicating that these parameters are useful for comparing the product life of MLCCs. These results will be reported in a future Vamas Report.

References

- 1) JIS C 5101-22: 2014, IEC 60384-22: 2011.
- 2) JIS R 1625: 2010.
- 3) C. A. Randall, R. Maier, W. Qu, K. Kobayashi, K. Morita, Y. Mizuno, N. Inoue and T. Oguni: *J. Appl.Phys.* **113**, 014101 (2013).